

Quasiparticle bands and superconductivity in bilayer cuprates.

A.I. Liechtenstein, O. Gunnarsson, O.K. Andersen, and R.M. Martin*
Max-Planck-Institut für Festkörperforschung, Heisenbergstr.1, D-70569 Stuttgart, FRG
 (1 September 1995)

We analyze the generic features of the energy spectrum for two coupled CuO_2 layers with a realistic extended Hubbard model. The quasiparticle bands exhibit flat regions near X(Y) points in the Brillouin zone with a large reduction of the bonding-antibonding splitting, and pinning of *extended* van-Hove singularity to the Fermi level, which is more efficient for a bi-layers than for a single layer. In contrast to the results with simpler models, the superconducting temperature for $d_{x^2-y^2}$ pairing is not lowered by the bi-layer hopping.

PACS numbers: 71.10.+x, 74.20.Mn

The role of multiple layers in the high-temperature superconductors continues to be one of the most intriguing puzzles, with many conflicting proposals and interpretations. One proposal is that superconductivity is enhanced by electronic correlations which are argued to greatly reduce single-particle hopping between layers while allowing *pair*-tunneling [1]. Angle-resolved photoemission (ARPES) studies [2,3] of the energy spectrum near the Fermi energy for bi-layer materials can in principle answer the questions of the nature of the bonding and antibonding bands near the Fermi level. However, one recent ARPES experiment [3] resolved only one CuO_2 band at the Fermi surface in BSCO-2212, supporting the idea of a greatly reduced interlayer hopping, whereas another measurement [2] reports two Fermi sheets, in general agreement with the predictions of band structure calculations. In addition, there is evidence for important effects of coupling between the layers in bilayer systems. Neutron scattering experiments see maximum intensity for spin scattering for wave vectors the $q_z \sim \pi/L$, where L is the interlayer spacing, for both the antiferromagnetic insulator and in the superconductor [4].

A generic feature which has emerged from the ARPES experiments [2,3] is a “flat-band” or “extended van-Hove singularity” which is “pinned” to the Fermi level for different hole dopings. Bifurcated saddle points very close to the Fermi level had, in fact, been predicted by LDA calculations for YBCO-123 [5] and caused by dimpling of the CuO_2 planes [6]. The flat band observed by ARPES has also been attributed to many-body effects [7–9], and a number of studies have been done for correlated electronic states in a single CuO_2 plane. The flat region in the quasiparticle spectrum has been proposed to be a “fermion condensate” [10,11], or a non-Fermi liquid area formed in $(\mathbf{q}, \omega)$ space near two-dimensional van-Hove singularity [12]. The one-band [7,9] and three-band [13] Hubbard models as well as t-J model [8] show a flat quasiparticle band just below the Fermi energy, which has an “extended” van-Hove singularity near the X($\pi, 0$)-point, due to antiferromagnetic spin fluctuations. The same antiferromagnetic fluctuations at $\mathbf{q} \approx (\pi, \pi)$ lead to $d_{x^2-y^2}$

superconductivity [14] with a relatively high transition temperature. For the two-plane Hubbard model [15,16] with a simple tight-binding spectrum a reduction of superconducting correlations was found due to the inter-layer coupling.

In this paper we study the bi-layer Hubbard model with realistic LDA derived hopping integrals. Combination of this realistic tight-binding (TB) model with many-body effects accounts for anomalous properties of cuprate superconductors. Thus in the normal state of our BSCO model, many body effects strongly reduce the splitting between the bonding and antibonding bands in the regions in the $\mathbf{k}$ -space where the one-body splitting is large, leading to flat bands near the chemical potential to within an energy of order room temperature. On the other hand, in the regions where the many-body effects are small, there is also little splitting in the one-particle spectrum, due to geometry of the bi-layer bonding in the cuprates. We analyze the pinning of the chemical potential to these van-Hove singularities in the case of a mono- and bi-layer model for different hole dopings. A calculation of the superconducting transition temperature shows robust stability of the $d_{x^2-y^2}$ state in the “three-dimensional” bi-layer case.

Let us start with the Hubbard hamiltonian for a bilayer CuO_2 model:

$$H = \sum_{i\alpha j\beta\sigma} t_{i\alpha,j\beta} c_{i\alpha\sigma}^\dagger c_{j\beta\sigma} + U \sum_{i\alpha} n_{i\alpha\uparrow} n_{i\alpha\downarrow} - \mu \sum_{i\alpha} n_{i\alpha\sigma},$$

here $t_{i\alpha,j\beta}$ are the hopping integrals which gives the energy bands $\varepsilon_n(\mathbf{k})$, $i(j)$ are the site indices inside the plane and $\alpha(\beta)$ are the plane indices, U is the on-site Coulomb repulsion and μ is the chemical potential. Due to the mirror plane symmetry for the bilayer [6] we can define bonding (+) and antibonding (−) electron bands $\varepsilon_+(\mathbf{k})$ and $\varepsilon_-(\mathbf{k})$, where $\mathbf{k}$ is a vector in the two dimensional Brillouin zone. This symmetry also holds for the quasiparticles excitation spectrum of the full interacting system. For our studies we have used different schemes which range from the simplest model (only nearest-neighbor

hopping in-plane and between planes) to realistic four- and eight-band models, obtained by integrating out the high-energy degrees of freedom from the full LDA calculations for cuprate superconductors [6].

For BSCO bi-layer materials we use a four-band Hamiltonian [17], which includes the standard Cu- $d_{x^2-y^2}$, and O- p_x, p_y orbitals, plus the “Cu-s” orbital which has also some Cu- d_{z^2} character. The last band is needed because the standard 3-band model does not give an adequate description of the valence band and the Fermi surface [17]. The Cu-s orbital provide the 2nd and 3rd nearest neighbor (t' and t'') intra-plane hopping integrals, as well as the hopping between the CuO₂ planes in the low-energy Hamiltonian H . Diagonalization of its first term yields the (simplified) “LDA bands”:

$$\varepsilon_{\pm}(\mathbf{k}) = -2t(\cos k_x + \cos k_y) - 4t' \cos k_x \cos k_y - 2t''(\cos 2k_x + \cos 2k_y) \mp t_{\perp}(\cos k_x - \cos k_y)^2/4.$$

Note that the interlayer hopping is anisotropic with the maximum splitting of $\varepsilon_+(\mathbf{k})$ and $\varepsilon_-(\mathbf{k})$ at the X($\pi, 0$) and Y($0, \pi$) points and no splitting in the direction from $\Gamma(0, 0)$ to M(π, π). We chose values of the tight-binding parameters for BSCO: $t = 0.5$ eV, $t'/t = -0.3$, $t''/t' = 0.2$ and $t_{\perp} = 0.15$ eV, close to the LDA parameters [17]. The total band width is $8t = 4$ eV, and the bonding-antibonding splitting at the X-point is $2t_{\perp} = 0.3$ eV. The screened electron-electron interaction parameter for Cu_d orbitals obtained in the constrained LDA calculations for cuprate is 7-8 eV [18]. Since the Cu_d character at the Fermi surface is approximately 65% [17] the effective U is reduced by 0.65^2 and we used in the present study $U = 3.2$ eV. This is a bit less than the band width, but general results are not very sensitive to the real U -values. Note that most many-body Monte-Carlo calculations [7,9,16] use only a simple tight-binding model: single - t parameter and isotropic $t_{\perp}$. We believe that in the cuprate system both many body effects and the band dispersion play a crucial role.

We used the conserving fluctuation-exchange (FLEX) approximation [19], which gives an energy spectrum for CuO₂ plane almost identical to Quantum Monte Carlo results [13]. We calculate the self-consistent one-electron Green’s function in the normal state:

$$G_{\pm}(\mathbf{k}, \omega_n) = \frac{1}{i\omega_n - [\varepsilon_{\pm}(\mathbf{k}) - \mu] - \Sigma_{\pm}(\mathbf{k}, \omega_n)},$$

where $\Sigma_{\pm}(\mathbf{k}, \omega_n)$ are bonding and antibonding self-energies and $\omega_n = (2n+1)\pi T$ are the fermion Matsubara frequencies with n an integer and T the system temperature. It is convenient to introduce the simple notation: $k = (\mathbf{k}, \omega_n)$ and $\sum_k = \frac{T}{2N} \sum_{\mathbf{k}, \omega_n}$, where N is the total number of momentum points. The straightforward generalization of the FLEX approximation [19] to the case of a bilayer two-band Hubbard model gives the following

equation for the self-energy:

$$\Sigma_{\pm}(k) = \sum_q [V_+(q)G_{\pm}(k-q) + V_-(q)G_{\mp}(k-q)],$$

where the contribution to effective potential $V_{\pm}(q) = V_{\pm}^s(q) + V_{\pm}^c(q)$ from spin and charge fluctuation are:

$$V_{\pm}^s = \frac{3}{2} \frac{U^2 \chi_{\pm}}{1 - U \chi_{\pm}} - V_{\pm}^{dc}, \quad V_{\pm}^c = \frac{1}{2} \frac{U^2 \chi_{\pm}}{1 + U \chi_{\pm}} - V_{\pm}^{dc},$$

here $V_{\pm}^{dc} = \frac{1}{2} U^2 \chi_{\pm}$ is the double counted contribution and $V_{\pm}(q)$ is defined self-consistently thorough particle-hole susceptibility for bi-layer:

$$\chi_{\pm}(q) = - \sum_k [G_+(k)G_{\pm}(k+q) + G_-(k)G_{\mp}(k+q)].$$

We solve the nonlinear integral FLEX-equations using the fast Fourier transform (FFT) method [20] on the discrete mesh of 64×64 momenta in the two dimensional Brillouin zone and 600-900 Matsubara frequencies with the cutoff of 20-30 eV (which corresponds to the temperature range of 80-200K). Analytical continuation on the real axes was done by Padé approximation. The calculations have been carried out for different hole concentrations: $\delta = 0.1 - 0.4$ per plane.

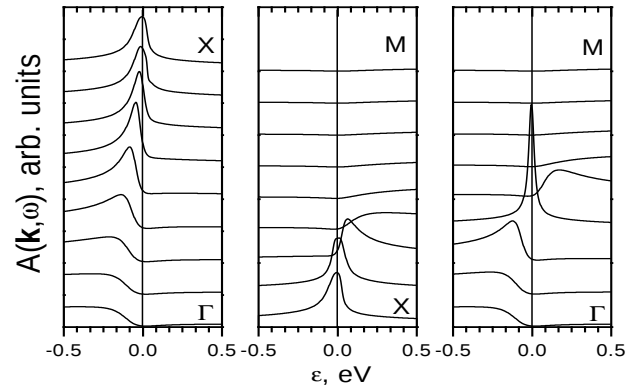


FIG. 1. The bi-layer spectral function for different directions in the Brillouin zone ($\delta = 0.25$, $T = 150$ K).

The spectral function $A(\mathbf{k}, \omega) = -1/\pi \text{Im}(G_+(\mathbf{k}, \omega) + G_-(\mathbf{k}, \omega))$ for hole doping $\delta = 0.25$ per CuO₂ and $T = 150$ K is shown in Fig.1 for Γ -X-M directions. One sees that there is only a single peak with a “non-Lorentzian” behavior crossing the Fermi level. In fact there are two bands with the large renormalization of the interlayer splitting from 300 meV to 40 meV, and there is large broadening at the actual temperature of the measurement in the normal state.

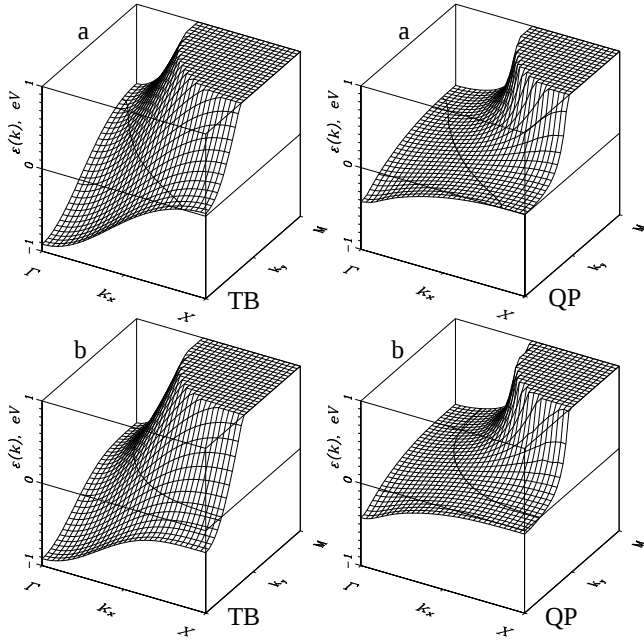


FIG. 2. Energy spectrum for $U=0$ (TB) and $U \neq 0$ (QP) for the antibonding (top) and bonding (bottom) bands.

This is illustrated in Fig.2, which shows a comparison of the pure tight-binding spectrum ($U=0$) and the quasiparticle spectrum (QP) for $\delta = 0.25$ for the bonding (b) and antibonding (a) bands together with corresponding Fermi-surface (zero-energy contour). The quasiparticle dispersion $\varepsilon_{\pm}^{QP}(\mathbf{k})$ have been determined through the maximum in the spectral function $A_{\pm}(\mathbf{k}, \omega)$. Note that already the TB (or LDA) bands differ substantially from the simple model with only one hopping - t : the position of the saddle points at the X and Y points is lower (for “ t -model” they are located at the middle of the band i.e. at 1 eV in Fig.2). This TB-spectrum changes the topology of the Fermi surface, and makes the hole doped and the electron doped situations quite different (as it should be experimentally [2]) and suppresses the nesting near half-filling. The last effect increases the width of a susceptibility peak near M(π, π) point and reduces the antiferromagnetic spin-correlation length from ≈ 3 to ≈ 1 one lattice spacing. This leads to the suppression of the “shadow bands” [21] in the quasiparticle spectrum which occur in the simpler model with $t' = t'' = 0$ and small doping $\delta \approx 0.1$ [22].

A more important consequence of t' and t'' is related to the increased flatness of the van-Hove singularities in the direction towards Γ , which leads to a larger phase space for the spin and charge excitations. This results in a drastic renormalization of the energy spectrum (Fig.2), mainly due to spin-fluctuation effects [13]. The quasiparticle bands exhibit flat regions near X(Y) points in the Brillouin zone with a large reduction of the bonding-antibonding splitting. Note that the susceptibility for anti-ferromagnetic coupling across the bi-layer $\chi_{-}(q)$ ex-

ceeds that $\chi_{+}(q)$, for ferromagnetic coupling and near $\vec{q} = (\pi, \pi)$ the difference could be even an order of magnitude for $t' = t'' = 0$, reflecting the enhancement of the antiferromagnetic fluctuations between the layer [4]. The Fermi surface is similar to the LDA, but the large flattening of the quasiparticle bands and the broadening of the spectral function [10] is not properly described in LDA.

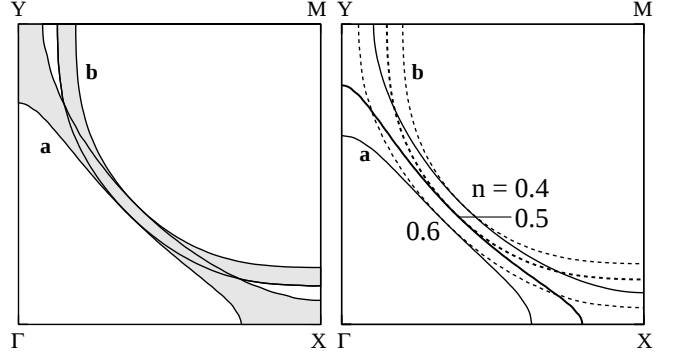


FIG. 3. Fermi surface for $\delta = 0.25$, $T=150$ K: temperature broadening (left) and constant occupation number contours (right).

We plot in Fig.3 the “temperature” smeared Fermi surface ($\mu = \pm T$ for $T = 150$ K) and constant occupation number contours: $n(\mathbf{k}) = \sum_n A(\mathbf{k}, \omega_n)$ [23] with $n_0=0.5$ corresponding to the Fermi surface. Note the extensive regions of nearly equal occupation ≈ 0.5 near the X and Y points. It is clear that the difference between the bonding and antibonding Fermi surface sheets for the BSCO model is very small and hard to detect experimentally [2,3]. We believe that the “shadow band” obtained in the recent ARPES experiment [3] is related to the large dark region near X(Y)-point for the antibonding bands. This flat region of the quasiparticle spectrum within the room temperature scale from the Fermi level gives the anomalous linear dependence of the self energy on temperature and frequency, just from the “phase-space” argument [11,24], detected numerically near X and Y points [22].

In order to show more clearly the formation of the flat quasiparticle band in the bi-layer system we plot in the Fig.4 the TB and QP spectrum for $\delta = 0.35$ where the Fermi level is approximately between bonding and antibonding bands at X. While the Fermi-level crossing-points are nearly the same in the TB and QP bands, the bonding and antibonding QP bands are “pinned” to the Fermi level within room temperature scale. In other words, the system has increased the spin and charge fluctuations by pinning the saddle points to the Fermi level and forming the extended van-Hove singularities instead of the standard renormalization of the spectrum only in the small region near the Fermi surface.

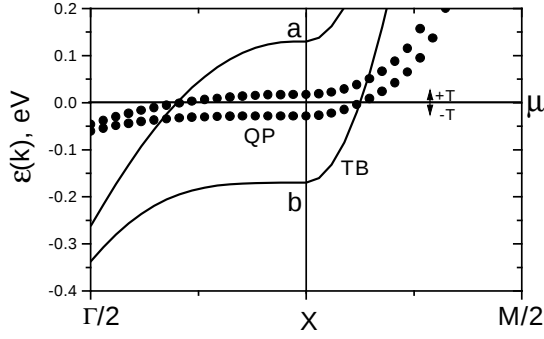


FIG. 4. Energy spectrum for TB and QP near X-point. Arrows indicate the room-temperature scale, $\Gamma/2 \equiv (\pi/2, 0)$, $M/2 \equiv (\pi, \pi/2)$ ($\delta = 0.35$, $T = 150$ K).

We have analyzed the effect of the saddle-points pinning to chemical potential for the monolayer ($t_{\perp} = 0$) and the bilayer models. The energy position of the saddle-point at X with respect to the Fermi level for the TB- and QP-spectrum as functions of the hole doping shown in the Fig.5. The antibonding QP-band for the bi-layer model (Bi-a) stays within the ± 5 meV for large hole concentration range $0.1 < \delta < 0.3$ per CuO_2 . Such a pinning effect is less pronounced in the monolayer (Fig.5).

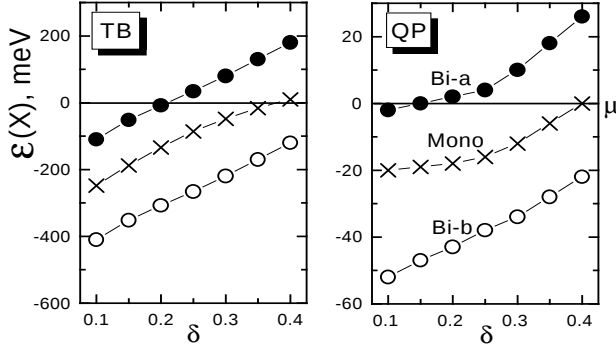


FIG. 5. Position of the saddle point at X relative to Fermi level for the TB and QP bands. Note the different scales.

The many-body reduction of the interlayer splitting also increases the quasiparticle density of states in the bi-layer and could help the formation of “three-dimensional” superconducting state. We find the superconducting transition temperature by solving the linearized Eliashberg equation for the singlet order parameters in the bi-layer model [15]. The critical temperature is defined via the maximum eigenvalue: $\lambda_{\max}(T_c) > 1$ of the following superconducting kernel:

$$R_{k'k} = - \begin{pmatrix} V_+^{sc} G_+(k) G_+(-k) & V_-^{sc} G_+(k) G_+(-k) \\ V_-^{sc} G_-(k) G_-(-k) & V_+^{sc} G_-(k) G_-(-k) \end{pmatrix},$$

where $V_{\pm}^{sc} = V_{\pm}^s(k' - k) - V_{\pm}^c(k' - k) + U$. We find that the superconducting $d_{x^2-y^2}$ state, which is symmetrical with respect to the mirror plane between the bi-layer, is indeed quite stable. The transition temperature for $\delta = 0.2$ is about 90 K (or $T_c = 0.015t$), which is almost the same as

for single layer (within one percent). The theoretical superconducting temperature for a LSCO-model [25] with a nested Fermi surface is a bit higher. If one takes into account the large order-parameter fluctuations which are expected to reduce T_c in the single layer [26], we can expect higher T_c 's in the bi-layer systems.

We have repeated the calculations for the YBCO eight-band TB-model [6] and found that the “bifurcated” saddle points in the TB-spectrum helps to create the extended anisotropic van-Hove singularity. In the YBCO model interlayer splitting is reduced by only a factor of two and could be in principle detected by ARPES measurements.

In conclusion, we have shown that the generic feature of bi-layer as well as mono-layer cuprate is the formation of extended van-Hove singularities near the chemical potential on the scale of the temperature, which occurs more readily in bi-layers. This leads to large areas of the Brillouin zone with nearly constant occupation ≈ 0.5 , which can explain the anomalous normal state properties and lead to enhanced $d_{x^2-y^2}$ superconductivity.

We acknowledge stimulating conversations with P.W. Anderson, K.B. Efetov, V.A. Khodel and M.C. Schabel.

* On leave from: UIUC at Urbana-Champaign.

- [1] S. Chakravarty, A. Sudbø, P.W. Anderson, and S. Strong, *Science*, **261**, 337 (1993)
- [2] Z.-X. Shen *et al.*, *Science*, **267**, 343 (1995).
- [3] H. Ding *et al.*, *Phys. Rev. Lett.* **74**, 2784 (1995); H. Ding, A.F. Bellman *et al.*, preprint.
- [4] J.M. Tranquada *et al.*, *Phys. Rev. B* **46**, 5561 (1992).
- [5] O.K. Andersen *et al.*, *Physica C* **185-189**, 147 (1991).
- [6] O.K. Andersen *et al.*, *Phys. Rev. B* **49**, 4145 (1994).
- [7] N. Bulut *et al.*, *Phys. Rev. B* **50**, 7215 (1994).
- [8] E. Dagotto *et al.*, *Phys. Rev. Lett.* **73**, 728 (1994).
- [9] R. Preuss *et al.*, *Phys. Rev. Lett.* **75**, 1344 (1995).
- [10] V.A. Khodel *et al.*, *JETP Lett.* **51**, 553 (1990).
- [11] P. Nozieres, *J. Phys.* **2**, 443, 1992.
- [12] I.E. Dzyaloshinskii, *Sov. Phys. JETP* **66**, 848, 1987.
- [13] R. Putz, R. Preuss *et al.*, preprint.
- [14] D.J. Scalapino, *Physics Reports*. **251**, 1 (1994).
- [15] N. Bulut *et al.*, *Phys. Rev. B* **45**, 5577 (1992).
- [16] R.T. Scalettar *et al.*, *Phys. Rev. B* **50**, 13419 (1994).
- [17] O.K. Andersen *et al.*, *J. Phys. Chem. Solids*, (1995).
- [18] A.K. McMahan *et al.*, *Phys. Rev. B* **38**, 6650 (1988).
- [19] N.E. Bickers *et al.*, *Annals of Physics*, **193**, 206 (1989).
- [20] J.W. Serene *et al.*, *Phys. Rev. B* **44**, 3391 (1991).
- [21] A.P. Kampf *et al.*, *Phys. Rev. B* **42**, 7967 (1990).
- [22] M. Langer, J. Schmalian *et al.*, preprint.
- [23] M. Randeria *et al.*, *Phys. Rev. Lett.* **74**, 4951 (1995)
- [24] S. Gopalan *et al.*, *Phys. Rev. B* **46**, 11798 (1992).
- [25] P. Monthoux *et al.*, *Phys. Rev. Lett.* **72**, 1874 (1994).
- [26] P.A. Lee and N. Read, *Phys. Rev. Lett.* **25**, 2691, 1987.